



DRAFT EAST AFRICAN STANDARD

Mattresses — Specification – Part 1: Flexible Polyurethane foams

EAST AFRICAN COMMUNITY

Copyright notice

This EAC document is copyright-protected by EAC. While the reproduction of this document by participants in the EAC standards development process is permitted without prior permission from EAC, neither this document nor any extract from it may be reproduced, stored or transmitted in any form for any other purpose without prior written permission from EAC.

Requests for permission to reproduce this document for the purpose of selling it should be addressed as shown below or to EAC's member body in the country of the requester:

© East African Community 2022 — All rights reserved
East African Community
P.O. Box 1096,
Arusha
Tanzania
Tel: + 255 27 2162100
Fax: + 255 27 2162190
E-mail: eac@eachq.org
Web: www.eac-quality.net

Reproduction for sales purposes may be subject to royalty payments or a licensing agreement. Violators may be prosecuted.

Foreword

Development of the East African Standards has been necessitated by the need for harmonizing requirements governing quality of products and services in the East African Community. It is envisaged that through harmonized standardization, trade barriers that are encountered when goods and services are exchanged within the Community will be removed.

The Community has established an East African Standards Committee (EASC) mandated to develop and issue East African Standards (EAS). The Committee is composed of representatives of the National Standards Bodies in Partner States, together with the representatives from the public and private sector organizations in the community.

East African Standards are developed through Technical Committees that are representative of key stakeholders including government, academia, consumer groups, private sector and other interested parties. Draft East African Standards are circulated to stakeholders through the National Standards Bodies in the Partner States. The comments received are discussed and incorporated before finalization of standards, in accordance with the Principles and procedures for development of East African Standards.

East African Standards are subject to review, to keep pace with technological advances. Users of the East African Standards are therefore expected to ensure that they always have the latest versions of the standards they are implementing.

The committee responsible for this document is Technical Committee EASC/TC 069, *Organic and Inorganic chemicals*.

Attention is drawn to the possibility that some of the elements of this document may be subject of patent rights. EAC shall not be held responsible for identifying any or all such patent rights.

DEAS 1115 consists of the following parts, under the general title *mattresses — Specification —*:

- Part 1: *Flexible polyurethane foams*
- Part 2: *Spring mattresses*

Mattresses — Specification – Part 1: Flexible polyurethane foams

1 Scope

This Draft East African Standard specifies requirements, sampling and test methods for flexible polyurethane foams mattresses. This standard does not cover orthopaedic and reconstituted mattresses.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 13934-2, *Textiles - Tensile properties of fabrics — Part 2: Determination of maximum force using the grab method*

ISO 13934-1, *Textile - Tensile properties of fabrics - Part 1: Determination of maximum force and elongation at maximum force using the strip method*

ISO 105-C10, *Methods for the determination of colour fastness of textile Materials to washing*

ISO 105-D01, *Method for determination of colour fastness of textile materials to dry cleaning*

3 Terms and definitions

For the purposes of this standard, the following terms and definitions shall apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1 block

mass of polyurethane foam formed by a free-rising foam process, in its original form prior to conversion.

3.2 bursting strength

the force required to rupture a fabric by distending it with pressure applied at right angles to the plane of the fabric

3.3 breaking strength

the maximum load (or force) supported by a specimen in a tensile test carried to rupture

3.4 defective

foam that fails in one or more respects to comply with the relevant requirements of the specification

3.5 polyurethane foam

the foam in which the polyol component is either polyether or polyester and produced by the reaction of polyol with an organic polyisocyanate in the presence of water, and that may include catalysts, surface-active agents, auxiliary blowing agents, fillers plasticizers, colourants, and any other additives that do not adversely affect the properties of the foam.

3.6 lot

not less than 1 m³ and not more than 100 m³ of foam of the same grade, and nominal dimensions, from one manufacturer, submitted at any one time for inspection and testing.

3.7 tick

a suitable outer cover that provides a comforting top layer of the mattress

3.8 warp

yarns / threads lying lengthways in a fabric as woven

3.9 weft

yarns / threads lying width ways in a fabric as woven (at right angles to the warp)

3.10 yarn

a generic term for a continuous strand of textile fibres or filaments without twisting, suitable for plying, knitting, braiding, weaving or otherwise intertwining to form a textile end product

3.11 tensile strength

stress at the breaking point of a specimen

3.12 elongation at break (ultimate elongation)

percentage strain produced in a specimen stretched to its breaking point

3.13 mattress

product providing a surface to sleep or rest upon, that is fit for use by human beings for a long period of time, consisting of a strong cloth cover filled with materials, and that can be placed on an existing supporting bed structure

3.14 polyurethane foam

cellular material produced by the reaction of a polyol with an organic isocyanate in the presence of water and that may include catalysts, surface active agents, auxiliary blowing agents, fillers, plasticizers, colourants and any other additives that do not alter the properties of the foam

4 Requirements

4.1 General requirements

4.1.1 The flexible polyurethane (polyether) foams mattresses shall be in four grades:

- a) Light duty grade
- b) Medium duty grade
- c) Heavy duty grade
- d) Superior heavy-duty grade

4.1.2 Flexible polyurethane foam shall not contain impurities or harmful residues such as amines which are volatile and driven off by heat generated in the formation of foam.

4.1.3 Adhesives used shall be either nitrile or neoprene based. If neoprene-based adhesives are used, they shall not have acidity of more than pH 3.5. The adhesives shall be able to withstand heat and moisture treatments as effectively as the foam itself.

4.1.4 Flexible Polyurethane foam core shall be clean in appearance and free from any objectionable odour and any residual amines likely to be harmful to human tissues.

4.1.5 The mattress core shall be flexible polyurethane foam of polyester or polyether type which is defined as expanded cellular product produced by interaction of polyhydroxy compound, water and isocyanate.

4.1.6 The Polyurethane foam mattress shall consist of cells of uniform characteristics which are essentially open and inter- connecting.

4.2 Specific requirements

4.2.1 Flexible polyurethane foam mattress shall comply with requirement specified in Table 1 when tested in accordance with method prescribed therein.

Table 1: Specific requirements for domestic flexible polyurethane foam mattresses

SL. No	Characteristic	Requirement	Test method	
i)	Compression set, %, max	Light duty grade	12	Annex A
		Medium duty grade	10	
		Heavy duty grade	8	
		Superior heavy-duty grade	5	
ii)	Density, kg/m ³ , min	Light duty grade	19.5	Annex B
		Medium duty grade	25	
		Heavy duty grade	30	
		Superior heavy-duty grade	35	
iii)	Durability, %, max	40	Annex C	
iv)	Tensile strength, N/mm ² , min	Light duty grade	0.069	Annex D
		Medium duty grade	0.083	
		Heavy duty grade	0.098	
		Superior heavy-duty grade	0.118	
v)	Elongation at break <ul style="list-style-type: none"> • Original, %, min. • After heat aging, retention of original, %, min. 	200	Annex D	
		80		
vi)	Heat ageing, retention of original, %, min	80	Annex E	
vii)	Tensile strength after humid aging, retention of original, %, min.	80	Annex F	
viii)	Porosity	report	Annex G	
ix)	Flammability	(a) No specimen shall burn for 3 min or more; and (b) No specimen shall burn beyond the gauge line	Annex H	
x)	Hardness factor, (all grades)	3.6 - 14.4	Annex I	

4.2.2 The cover of flexible polyurethane foam mattresses shall be of a woven ticking, or a knitted ticking and shall conform to the specific requirements given in Table 2 when tested in accordance with the methods prescribed therein.

Table 2 - Specific requirements for ticking of flexible polyurethane foam mattresses

SL. No	Characteristic		Requirement			Test method			
			Light	medium	Heavy and super heavy				
i)	Breaking strength (woven ticking) N, min.	Polyester	Warp	350	450	600	ISO 13934-1		
			Weft	280	300	350			
		Nylon	Warp	350	450	700			
			Weft	280	300	350			
		Cellulosic	Warp	250	300	450			
			Weft	160	200	280			
		Polyester/ Nylon/Cellulosic Blends	Warp	300	350	500			
			Weft	180	200	250			
		ii)	Bursting strength (knitted ticking), KPa, min.	Polyester	200			ISO 13934-2	
				Nylon	200				
Cellulosic	150								
Polyester/ Nylon/Cellulosic	160								
iii)	Mass in g/m ² (min.)		Light	medium	Heavy and super heavy	Annex J			
		Polyester	68	68	120				
		Nylon	68	68	120				
		Cellulosic	85	110	200				
		Polyester/ Nylon/Cellulosic Blends	60	80	150				
iv)	Colour fastness to washing	Change in colour, rating, min.	4			ISO105-C10			
		Staining of transfer cloths, rating, min							
v)	Colour fastness to dry-cleaning	Change in colour, rating, min.	4			ISO 105-D01			
		Staining of transfer cloths, rating, min							
vi)	Flammability	To comply with flammability requirements given in x) of table 1				Annex H			

4.2.3 When tested in accordance with Annex K, the mattress shall conform to the dimensions declared on the label subject to the following tolerance limits (mm)

- Length = 0 - +40 for 1800 – 2000
- Width = 0 - +10 for 750 – 900
- Width = 0 - +25 for 901 – 1350
- Length = 0 - +40 for 1351 – 2000
- Thickness = 0 - +5 for 750 – 150

4.2.4 Top skin of polyurethane foam mattress shall be:

- a) with a minimum density of 24kg/m;
- b) practically free from cracks; and
- c) with a minimum thickness of 1.5 mm

5 Packaging

Flexible polyurethane foam mattresses shall be individually wrapped in suitable materials that prevent any damage, gross and distortion to contents during storage and transportation.

6 Labelling

Each Flexible polyurethane foam mattresses shall be legibly and indelibly labelled, in English and/or any other official language (French, Kiswahili, etc) used in the importing East African Partner State with the following information:

6.1 on the outer upper waist of the mattress or a label attached on it:

- a) grade of foam mattress;
- b) nominal length, width and thickness;
- c) registered trade name of the product if any;
- d) name of the manufacturer;
- e) batch number/lot number;
- f) date of manufacture;
- g) country of origin; and
- h) disposal instructions and precautionary statements.

6.2 on the foam:

- a) grade of foam mattress;
- b) nominal length, width and thickness;
- c) name of the manufacturer;
- d) batch number/lot number; and
- e) country of origin.

7 Sampling

Representative samples shall be taken according to the sampling plan given in Table 4.

Each sample shall consist of the following:

- a) for inspection, a complete piece; and
- b) for testing, pieces of total volume of at least 0.01 m³.

Table 4 — Sampling plan

Number of mattresses in the lot	Number of samples to be selected
2 - 8	2
9 - 15	3
16 - 25	5
26 - 50	8
51 - 90	13
91 - 150	20

Annex A

(normative)

Compression Set Test

The test consists of maintaining the foam specimen under specified conditions of temperature and observing the degree of recovery within a specified time after release.

A.1 Apparatus

The apparatus consists of two flat plates of 200 mm x 200 mm, with appropriate spacers and clamps to keep the plates parallel to each other when clamped with specimen between the plates.

A.2 Test specimen

Cut the test specimen from a foam slab which has been cured for 48 hours at room temperature in such a way that the load is applied in the direction of the rise of the foam to get specimen of 50 mm x 50 mm x 25 mm. Test specimens shall be free from any contamination and skin on the vertical sides. When thin materials are to be tested, sufficient specimens of 50 mm x 50 mm shall be taken so that the sum of their thickness before compression is at least 25 mm. The specimens shall be plied together and interleaved with photographic glass-mounting slides where the number of plies is greater than two, and the complete assembly shall be treated during the test as single thick specimen.

Condition the test specimens at $27^{\circ}\text{C} \pm 2^{\circ}\text{C}$ and 65 ± 5 per cent relative humidity for 6 hours before testing. A minimum of 3 specimens shall be tested for 50 or 75 percent compression of its thickness. In special cases a compression of 90 per cent may be agreed upon.

A.3 Procedure

A soft material dial thickness gauge is used for measuring the thickness of the specimen. In case of thin material calculate the thickness of the foam by deducting the aggregate thickness of the glass slides from the measured total thickness of the assembly. The specimen shall then be put between the plates and with the help of spacers subjected to 50 per cent deflection. The whole assembly is then stored under standard atmospheric conditions for 70 hours or at $70^{\circ}\text{C} \pm 2\text{C}$ for 22 hours. After this duration, the plates are removed and the specimen is allowed to recover for at least 30 minutes under standard testing conditions.

The thickness is measured again with the soft material dial thickness gauge. The same procedure is followed for 75 or 90 per cent deflection.

A.4 Calculation and reporting

Compression set at the rate of 50 percent deflection

$$h_0 - h_{50} \times 100$$

Compression set at the rate of 75 percent deflection

$$h_0 - h_{75} \times 100$$

Compression set at the rate of 90 percent deflection

$$h_0 - h_{90} \times 100$$

where

h_0 is an original height of the specimen in mm,

h_{50} is a final height of the specimen in mm after 50 percent deflection test

h_{75} is a final height of the specimen in mm after 75 per cent deflection test

h_{90} is a final height of the specimen in mm after 90 per cent deflection test

Average of the values obtained from the three samples tested shall be reported.

Annex B

(normative)

Determination of density

B.1 Apparatus

B.1.1 Soft material thickness gauge for measurement of linear dimensions up to 100 mm with an accuracy of one percent.

B.1.2 *Balance*

Capable of weighing the test specimen to an accuracy of one per cent of the total mass.

B.2 Test specimen

Obtain test specimens, of regular shape not less than 100 mm x 100 mm x 100 mm, one each from top, middle and bottom portions of the foam slab with respect to direction of rise of foam, cured for 48 hours at room temperature. Condition the specimens for 6 hours at 27 °C ± 2°C and at 65 % ± 5 % relative humidity before testing.

B.3 Number of specimens

Unless otherwise specified three specimens shall be tested.

B.4 Linear dimension

B.4.1 *Measurement below 100 mm linear dimension*

Set the dial at zero. Place the specimen centrally below the foot. Lower the foot with the application of the specified load. Note the reading taking into account the metallic spacers used, if any. Repeat this thrice in each direction for every specimen.

B.4.2 *Measurement above 100 mm linear dimension*

Place the specimen on a plane table and measure the dimension with vernier caliper or steel tape accurately. Repeat this thrice for every specimen.

B.4 Procedure

Determine the linear dimensions as described in B.4.4.1 and B.4.4.2 Weigh the specimens on a balance with an accuracy of one per cent of the total mass.

B.5 Calculation

$$\text{Density (P) kg/m} = \frac{m}{v} \times 1\,000$$

where

m is a mass of specimen in g, and

V is a volume of the specimen in cm

B.6 Report

Report the mean density of the three specimens tested.

Annex C

(normative)

Durability Test

C.1 Test specimen

The test is conducted on a sample of the foam 15 in x 15 in x 4 in thick (381 mm x 381 mm x 120mm) and constructed in the same way as the mattress core (e.g. if the core is laminated, then the laminated test piece should be used).

C.2 Procedure

After conditioning, the block is supported on a smooth, horizontal and rigid surface, suitably vented to allow the escape of air. The block is then subjected to repeated indentation at a rate of 120 cycles per minute for 32 hours (230, 400 cycles). To prevent the block moving during pounding, cotton strips may be stuck to the bottom of the foam and held to the base plate with clips. The load applied by the indenter shall be measurable and the maximum load of the stroke is adjusted periodically to maintain, it at 70 kg.

The indenter shall be 8 in (203 mm) in diameter with rounding off radius of 1 in, ie. overall diameter of 10 in (254 mm) indentation hardness shall be read within 5 minutes of the end of pounding.

Annex D

(normative)

Tensile strength Test


D.1 Apparatus

The apparatus consists of a power-driven machine (medium load tensile tester) with the following provisions:

- a) sensitive dial indicator which remains at the point of maximum load after rupture of the specimen and measures the tension at the point,
- b) suitable grips for holding the specimen,
- c) rate of travel of power actuated grip shall be $500\text{mm} \pm 50 \text{ mm}$ per minute and uniform at all times and
- d) the total capacity of the tester be such that the ultimate load is at least one-fifth of the total capacity of the machine.

D.2 Test specimen

Punch the specimen in the shape of a dumb-bell shown in the figure D.1 below by means of a sharp die out of a foam sheet of 10mm or 20 mm thickness. The foam sheet shall be cut vertically in the direction of the rise of the foam with the help of a splitting machine, from the foam slab cured at room temperature for 48 hours. Condition the test specimen at $27^{\circ}\text{C} \pm 2\text{C}$ and 65 ± 5 percent relative humidity for 6 hours before testing. Three specimens shall be tested.

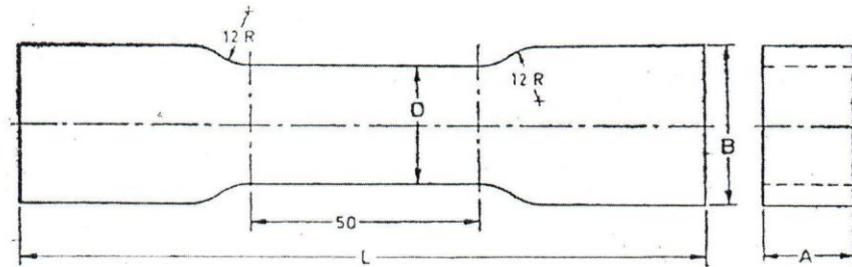

	A	B	D	L
Small	10	25	13	152
Large	2	3	2	152

All dimensions in millimeters.

Figure D.1 dumb-bell test piece

D.3 Procedure

D.3.1 Determine the thickness and width of the specimen accurately by means of a vernier caliper or soft material thickness gauge as described in clause 3. Make two-gauge marks 50 mm apart as shown in the figure.

D.3.2 Clamp the specimen in the grips. The minimum separation between the grips shall be 65 mm. Adjust the specimen symmetrically between the grips for uniform distribution of the tension applied over the cross-section.

D.3.3 Start the machine and note continuously the distance between the two-gauge marks and record the distance at rupture. Note the lead indicated on the dial.

D.5 Calculation and reporting

D.5.1 Tensile strength (β), $\text{N/mm}^2 = \frac{F_{max}}{A}$

where

F_{max} is a force at failure of the specimen in N, and

A is an original cross-sectional area in mm^2

D.5.2 Tensile stress (δ_t), $\text{N/mm}^2 = \frac{F_t}{A}$

where

F is a force at specified elongation in N, and

A is an original cross-sectional area in mm^2

D.5.3 Ultimate elongation (Elongation at Break)

$$\text{Ultimate elongation } (\epsilon_b) \text{ per cent} = \frac{L_b - L_0}{L_0} \times 100$$

where

L_b is a length between the gauge marks in mm at the time of failure, and

L_0 is an original length between the gauge marks in mm.

D.5.4 Report

Report the averages of the three-specimen tested

Annex E

(normative)

Heat ageing Test

Determine as in Annex D the tensile strength and elongation at break of five specimens that have been heat aged for 22 h in an air oven at 140 °C + 1 °C, and calculate the resistance to heat aging of the sample as

$$\text{Resistance to heat aging, retention of original, \%} = \frac{\text{value of tensile property of aged sample}}{\text{original value of the tensile property}} \times 100$$

Annex F

(normative)

Tensile after humid aging Test

Determine as in Annex D the tensile strength and elongation at break of five specimens that have been humid aged in dry steam at 105 °C + 1 °C for 3 h, dried at 70 °C to constant mass. Then calculate the resistance to humid aging of the sample as follows:

$$\text{Resistance to humid aging, retention of original, \%} = \frac{\text{value of tensile property of the aged sample}}{\text{original value of the tensile property}} \times 100$$

Annex G

(normative)

Porosity Test

G.1 Apparatus

The apparatus consists, essentially, of a specimen holder connected through a flow meter to a supply of clean dry air. The apparatus shall include means for precise control of air flow rate and a manometer connected between the specimen holder and the flow meter. The specimen holder shall consist of a circular container, of internal diameter 38 mm and depth 25 mm, that has an air inlet of diameter 25 mm in the centre of its base, and a cover with a central aperture of diameter 25 mm. The cover shall form an airtight seal with the top of the container, and the entire apparatus shall be free from leaks.

G.2 Test specimens

From the appropriate slab (see 8.2) cut four cylindrical specimens each of diameter 38 mm and height 25 mm.

G.3 Procedure

Level the manometer and set it at zero. Insert the test specimen holder and replace the cover. Turn on the air supply and adjust it to obtain a pressure in the apparatus (as recorded by the manometer) of 125 Pa. When the pressure reading is steady, note the rate of air flow recorded by the flow meter. Repeat the test with the remaining three specimens. Calculate the porosity of each specimen as follows:

$$\text{Porosity, m}^3/\text{s.m}^2 = 2\,040\,F$$

where,

F is the flow rate, in m³/s.

Record the mean of the four results as the porosity of the sample.

Annex H

(normative)

Test for flammability of polyurethane foam mattresses

H.1 Apparatus

An apparatus as shown schematically in Figure H.1 and consisting of a heat-resistant glass tube (chimney) in which a test specimen can be mounted, the base of the tube being connected to metered supplies of oxygen and nitrogen. The glass tube shall have a diameter of at least 75 mm and a height of at least 450 mm, and shall have at its base a bed of glass beads (or other inert particles) that will mix and distribute the incoming gases. The tube shall also contain a clamp that is capable of holding a test specimen (vertically) that the top of the specimen is at least 100 mm below the top of the tube.

The oxygen and nitrogen used shall be of commercial grade (or better) and shall be supplied to the base of the glass tube through individual metering devices that enable the volumetric flow of each gas to be measured with an accuracy of 1 % or better.

H.2 Test specimens

From the appropriate slab cut five specimens each of size 12.5 ± 0.5 mm x 12.5 ± 0.5 mm x 130 mm and draw a gauge line across each specimen 75 mm from the end that is to be positioned uppermost in the apparatus.

H.3 Procedure

Clamp a test specimen in the holder of the apparatus so that it is held vertically in the centre of the glass chimney. Open the valves of the gas cylinders and adjust the flow so that the oxygen content of the gas mixture is $20\% \pm 0.2\%$ and that the flow rate up the glass chimney (as calculated from the volumetric flow rate divided by the cross-sectional area of the chimney) is $40\% \pm 10\%$ mm/s. Allow the gas to flow for at least 30 s and then, using a small gas flame at the end of a tube, ignite the test specimen so that the whole of the upper surface is burning. Note whether the specimen burns for 3 min or longer and if not, whether or not the specimen has burned to below the 75 mm gauge line. Repeat the test with the remaining four specimens.

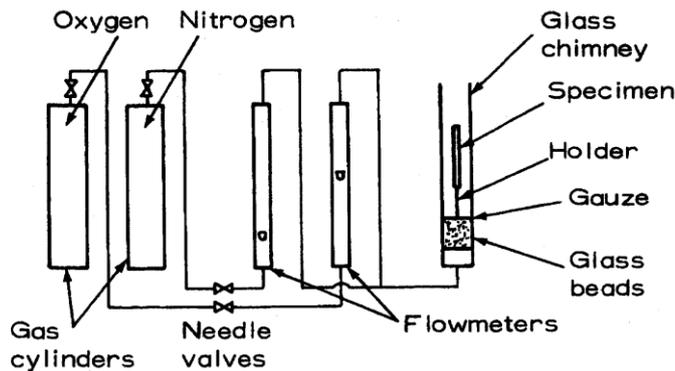


Figure H.1 — General arrangement of flammability test apparatus

Annex I

(normative)

Hardness factor Test

I.1 Apparatus

The miniflex CLD hardness tester

I.2 Test specimen

A foam sample of dimensions 100 mm x 100 mm x 50 mm will be used.

I.3 Procedure

The test procedure first measures the thickness of the foam sample (pre load). It is then compressed three times to 30 % of its original thickness (pre flex) at a defined speed.

Finally, the sample is compressed to 60 % of its original thickness and the force necessary to do this is measured and recorded. This force normally expressed as pressure in kilopascals (kPa) is the hardness value.

Hardness factor is obtained by referring to Table 2.

Annex J

(Normative)

Test method for mass per unit area

J.1 Principle

This method specifies the procedures for determining the mass per unit area of woven fabrics (including those of the stretch type), knitted fabrics, nonwoven fabrics, composite fabrics and narrow fabrics.

J.2 Apparatus

J.2.1 Table that has a smooth flat surface and is of a size that exceeds that of the fabric to be measured

J.2.2 Cutter, that is capable of cutting a square or circular specimen of area, 0.01m^2 to accuracy of 1 % or better.

J.2.3 Metal plate, that is 5 mm smaller than the cutter and that has a thickness of 10 mm

J.2.4 Balance, that is capable of determining the mass of the specimen to accuracy of 0.2 % or, in the case of 0.01m^2 specimens, to an accuracy of 0.001 g.

J.3 General

Condition the sample

Before testing, maintain all specimens for at least 16 h in an atmosphere having a relative humidity of wise $65\% \pm 2\%$ and a temperature of $23\text{ }^\circ\text{C} \pm 2\text{ }^\circ\text{C}$.

J.4 Procedure 1 - Full width specimen

J.4.1 Ensure that the fabric, which should preferably be selected from the middle of a piece, is not less than 0.5 m and not more than 4 m long, and lay it flat, and without tension, on the table.

J.4.2 Cut at both ends across the full width of the sample along parallel lines at right angles to the selvedge.

J.4.3 If the mass per unit area of a selvedge on a full – width piece appears to deviate appreciably from the mass per area of the body of the fabric, or if so agreed upon between the parties concerned, trim off the selvedge along the outermost threads of the body of the fabric and use only the body of the fabric for the determination of the mass per unit area.

J.4.4 Measure the width and length of the specimen.

J.5 Procedure 2 - For representative for large cuttings

J.5.1 Ensure that available cutting is representative of the sample.

J.5.2 Trim the cutting into a square or rectangular specimen by cutting along parallel lines at right angles to the warp (length) direction and at right angles to the weft (width) direction.

J.5.3 Measure the width and length of the specimen.

J.5.4 Use the balance to determine the mass of the specimen

J.6 Procedure 3 - For several small (0.01m^2) specimens

NOTE: On fabrics with large in-woven designs, which involve local areas of appreciably different mass per unit area, the use of procedure 1 or procedure 2 is preferable.

J.6.1 Cut at least three-square pieces, of side length of approximately 150 mm, from areas of the fabric selected to represent the samples as fully as possible but not within 50 mm of the selvedge.

J.6.2 Lay each piece flat, and without tension, on a suitable cutting surface. Place the metal plate and cutter on each piece in turn and cut out a 0.01 m² specimen from each piece, ensuring that no loss of threads occurs.

J.6.3 Use the balance to determine the mass of the 0.01 m² specimens, and calculate the mean mass.

J.7 Calculation

J.7.1 In the case of procedure 1 and procedure 2, calculate the mass per unit area M in grams per square metre, using the following formula:

$$M = \frac{m \times 1,000,000}{L \times w}$$

where

m is the mass of the specimen, in grams
 L is the length of the specimen, in millimeters; and
 w is the width of the specimen, in millimeters

J.7.2 In the case of procedure 3, calculate the mass per unit area (M in grams per square metre) by multiplying the mean mass (in grams) by 100.

Annex K

(normative)

Dimensions

K.1 Apparatus

K.1.1 Metre rule, a steel rule graduated in millimeters and accurate to 1 mm (or better).

K.1.2 Micrometer, a micrometer accurate to 0.01 mm (or better) with a presser foot of area at least 6.5 cm and capable of exerting a pressure of 100 ± 10 Pa.

K.2 Procedure

Measure the dimensions of each sample (using the steel rule for dimensions greater than 30 mm and the micrometer for dimensions not exceeding 30 mm).

Annex L
(informative)

Dimensions of polyurethane foam mattresses

The dimensions for the polyurethane foam mattresses may be as provided in Table L.1

Table L.1 - dimensions of flexible polyurethane foam mattresses

S/No.	Characteristic	Requirement, mm	Tolerance, mm
i)	Length	1800-2000	- 0 +40
ii)	Width	750 - 900	-0 +10
		901 - 1350	-0 +25
		1351- 2000	-0 +40
iii)	Thickness	75 -150	-0 +5

Bibliography

- [1] TZO 360:2021 *Flexible polyurethane foam mattresses - Specification*
- [2] TZO 359:1996 *Methods of test and sampling for flexible polyurethane foam*
- [3] KS 376-0:2013 *Flexible polyurethane (polyether) foams — Specification - Part 0: General requirements*
- [4] KS 376-1:2005 *Flexible polyurethane (polyether) foams — Specification - Part 1: Mattresses*
- [5] KS 376-2:1999 *Specification for flexible polyurethane foams - Part 2: Reconstituted flexible polyurethane foam*
- [6] US 202: 2021 *Textiles — Foam mattress — Specification*

DEAS 1115-1:2022 - FOR PUBLIC REVIEW ONLY